

# Interactions of cells with their environment; Engineering materials with biological recognition

---

- Last time:** Polyelectrolyte hydrogel swelling thermodynamics  
Applications of polyelectrolyte hydrogels: BioMEMS and drug delivery
- Today:** Biological recognition *in vivo*  
Engineering biological recognition of biomaterials: controlling cell adhesion, migration, and cytokine signaling
- Reading:** Y. Hirano and D.J. Mooney, 'Peptide and protein presenting materials for tissue engineering,' *Adv. Mater.* **16**(1) 17-25 (2004)  
Discher, Janmey, Wang, 'Tissue Cells Feel and Respond to the Stiffness of Their Substrate,' *Science* **310** 1139-1143 (2005))
- Supplementary Reading:** 'The Extracellular Matrix,' pp. 1124-1150, *Molecular Biology of the Cell*, Lodish et al.
- 

## ANNOUNCEMENTS:

# *In situ* formability: example: 'printable' gels

Collagen printed on an agarose gel substrate:



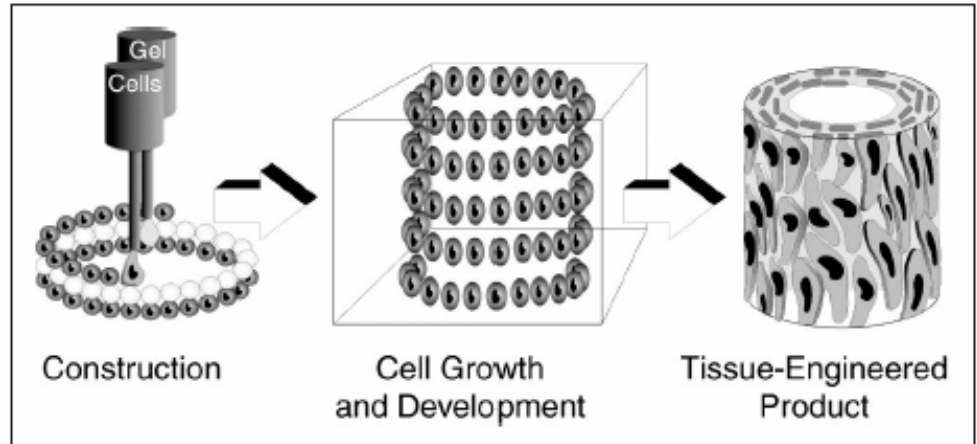


Figure 14 in Burg, K. J., and T. Boland. "Minimally Invasive Tissue Engineering Composites and Cell Printing." *IEEE Eng. Med. Biol.* 22, no. 5 (2003): 84-91.


# Formability of hydrogels for tissue engineering

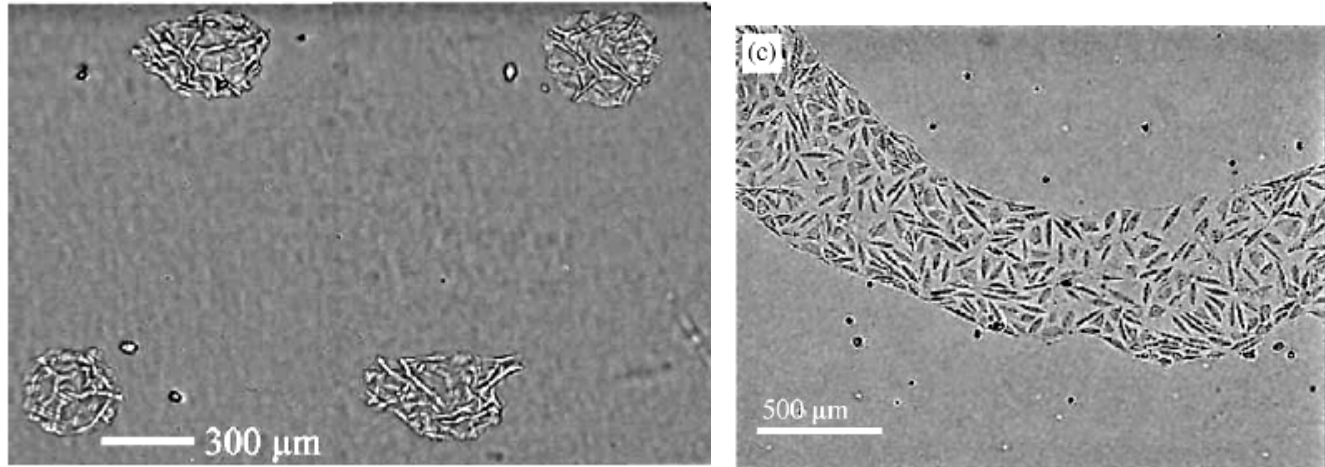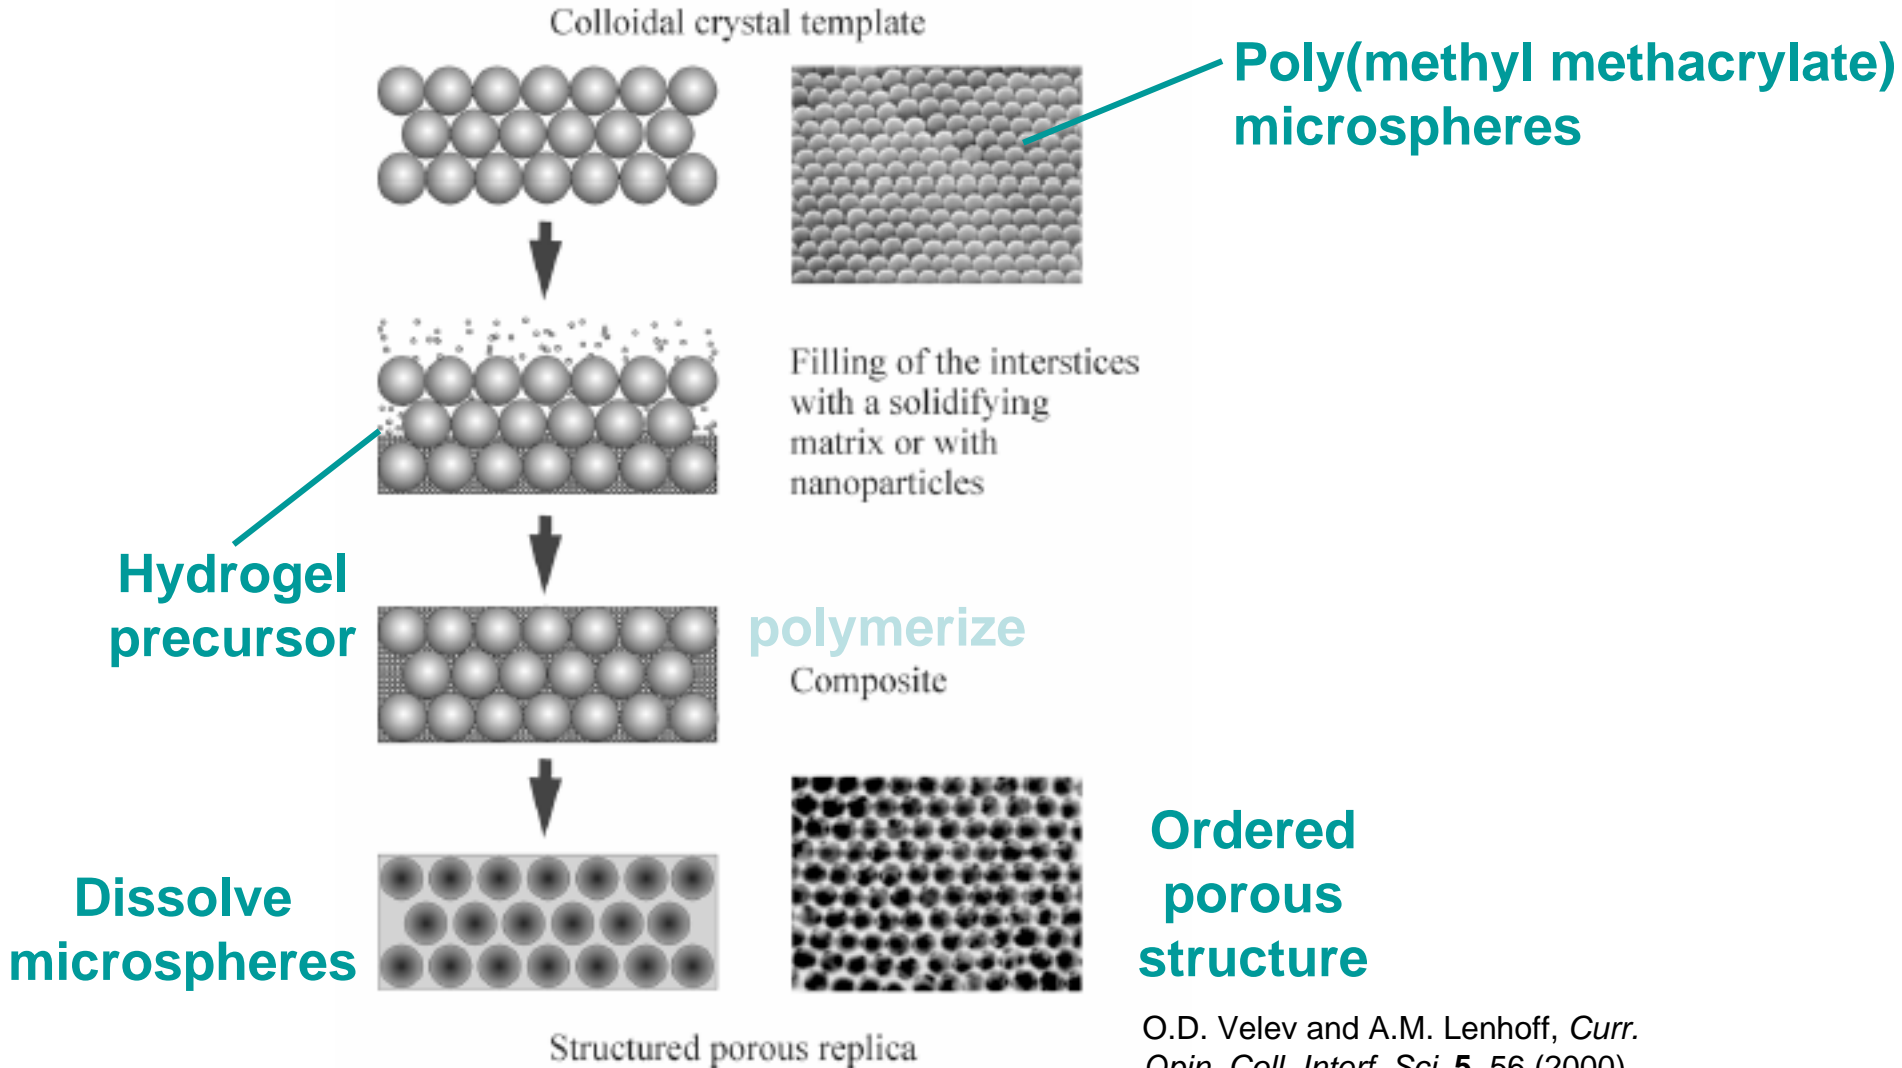

O.D. Velev and A.M. Lenhoff, *Curr. Opin. Coll. Interf. Sci.* **5**, 56 (2000)


## Tissue engineering

Brightfield image:

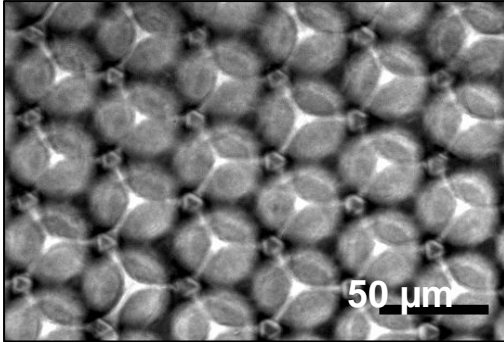


Confocal fluorescence:

1 unit = 20 μm

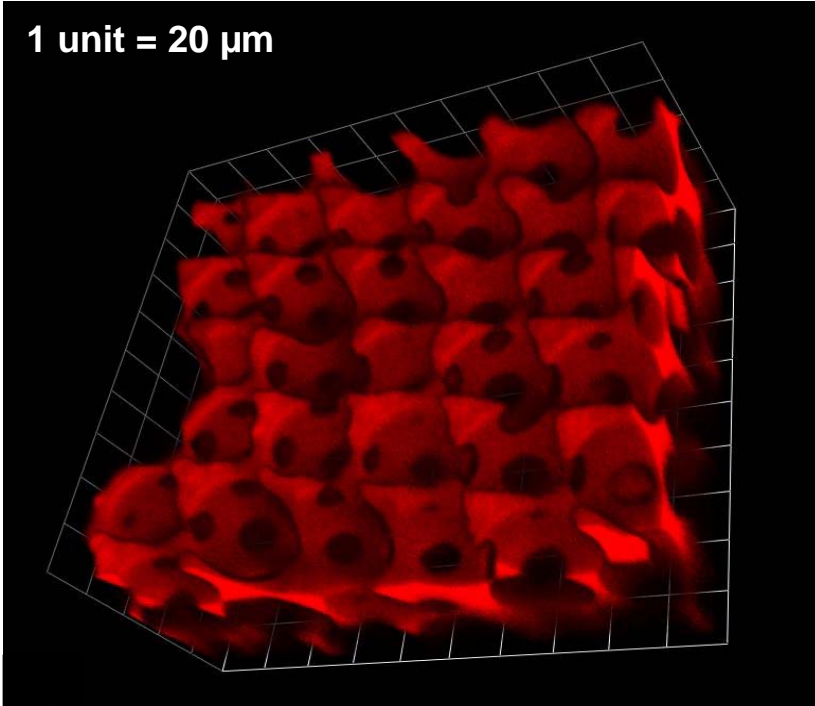


Scaffolds with ordered, highly interconnected porosity

## PEG hydrogel scaffolds

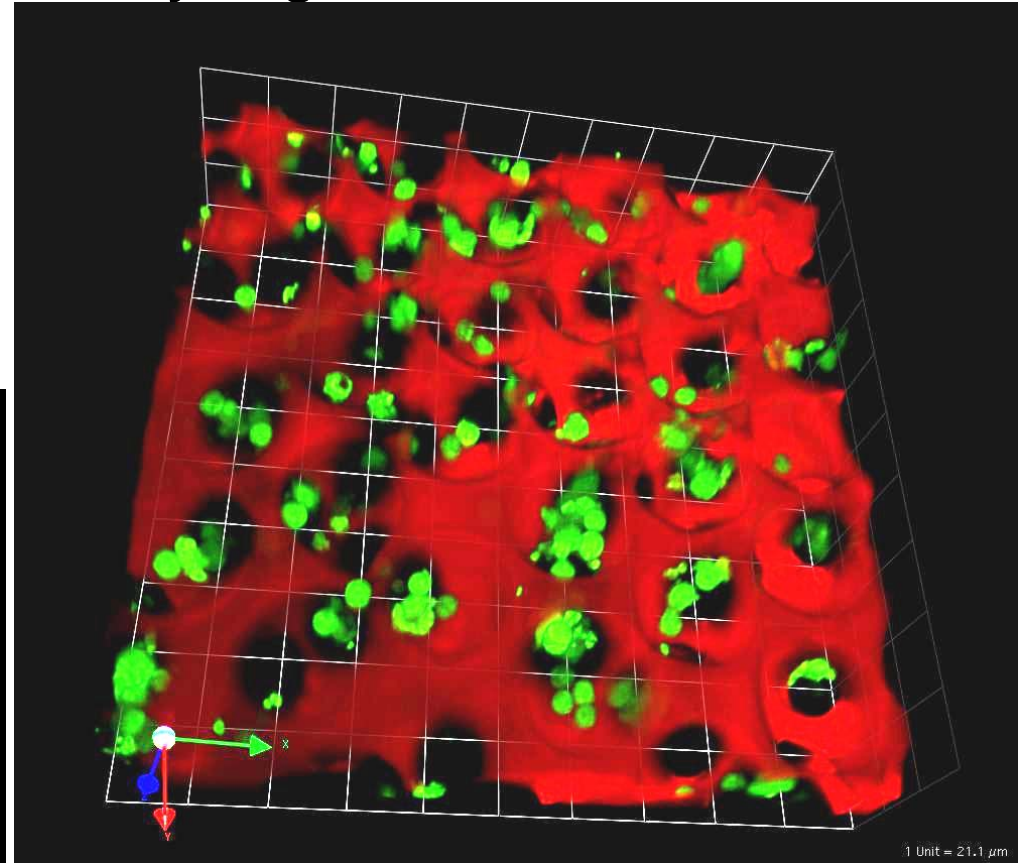

A. Stachowiak et al, *Advanced Materials* (2005)

# Degradable hydrogels: degradation by hydrolysis of cross-links (mechanism I)

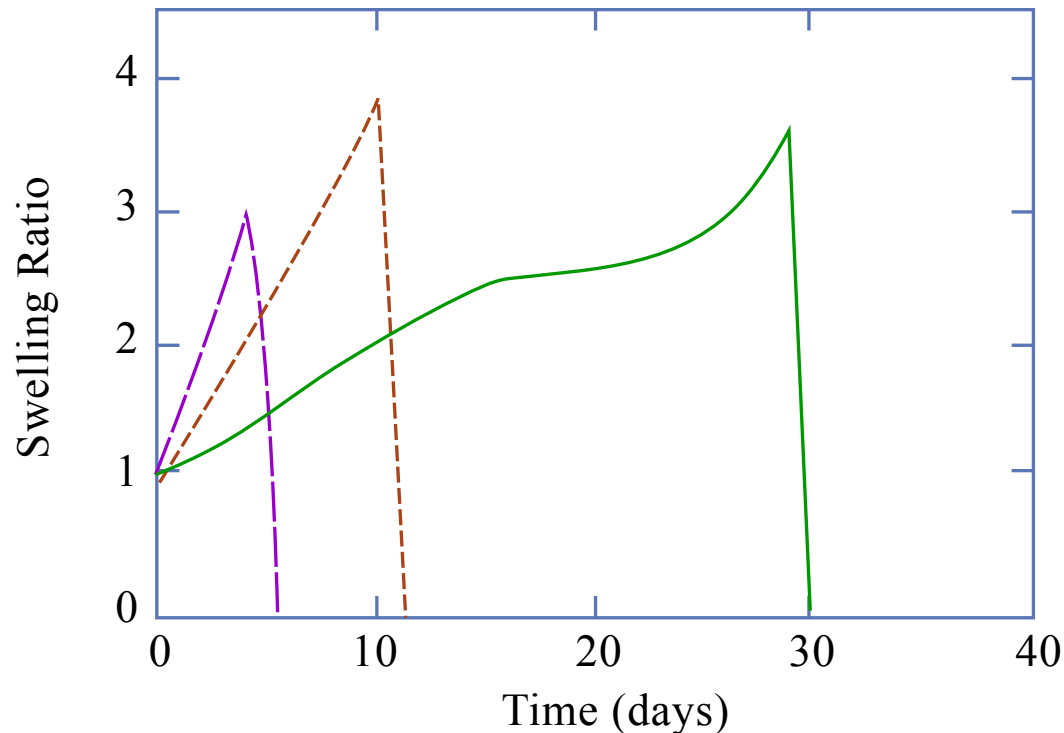Dextran-based degradable hydrogels:  
degradation by hydrolysis of cross-links

Swelling behavior of dex-HEMA (—), dex-lactate-HEMA (---) and dex-lactate<sub>2</sub>-HEMA (---) hydrogels in aqueous solution (pH 7.2, 37°C). The initial water content of the hydrogels was 80%, the degree of methacryloyl substitution was approximately 6.

Figure by MIT OCW.

# Tissue barriers/conformal coatings

## Applications: tissue barriers

### Tissue barriers and conformal coatings


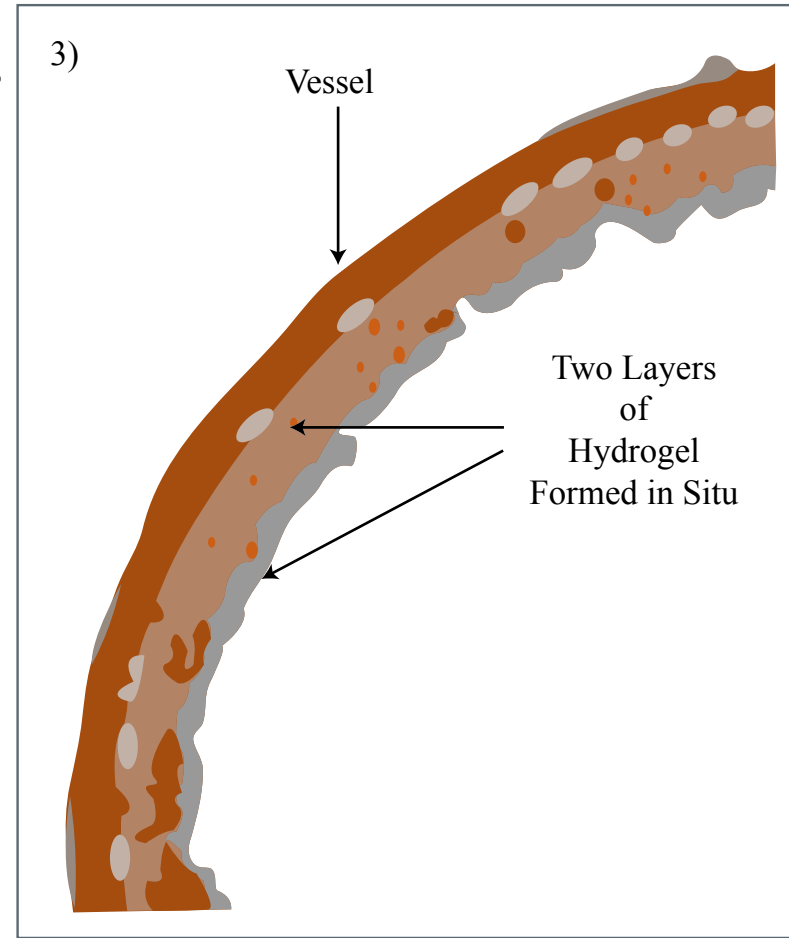



Figure by MIT OCW.  
(After An and Hubbell 2000)

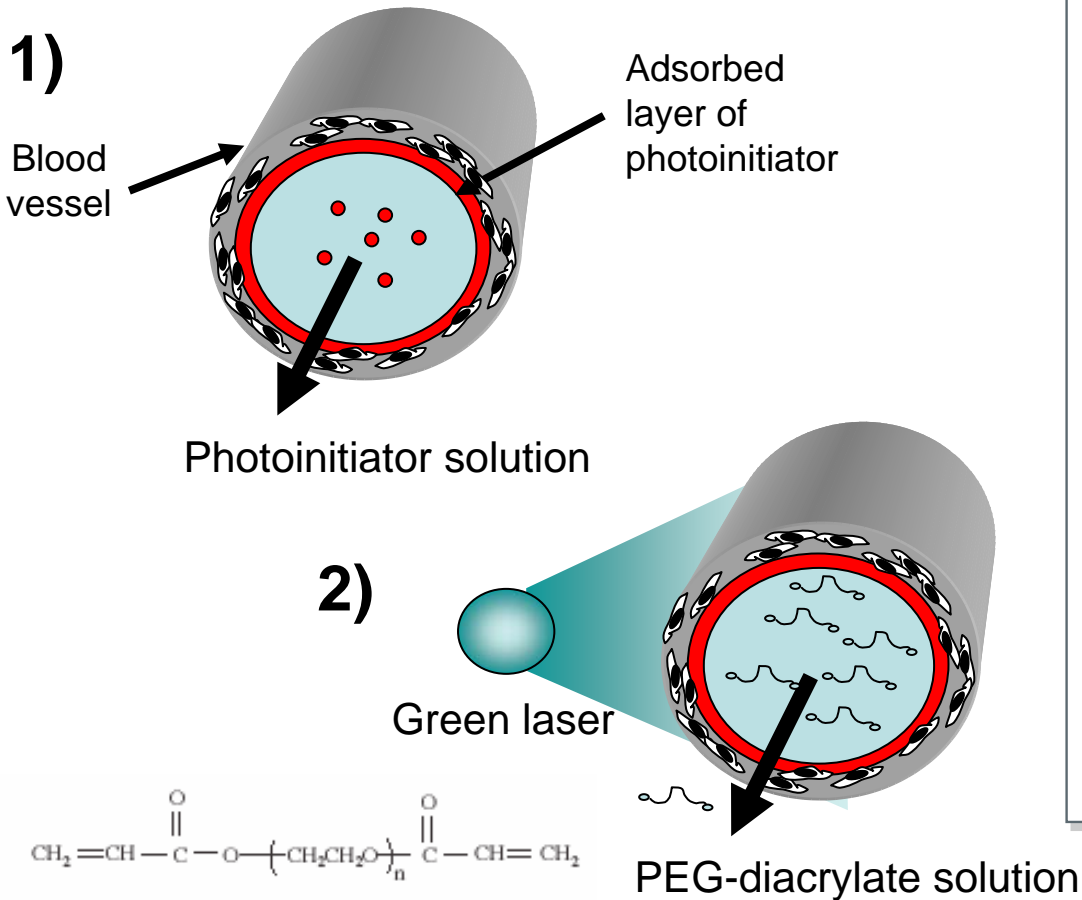


# Engineering Biological Recognition in Synthetic Materials

# Interactions of cells with their environment

Signals from extracellular environment:

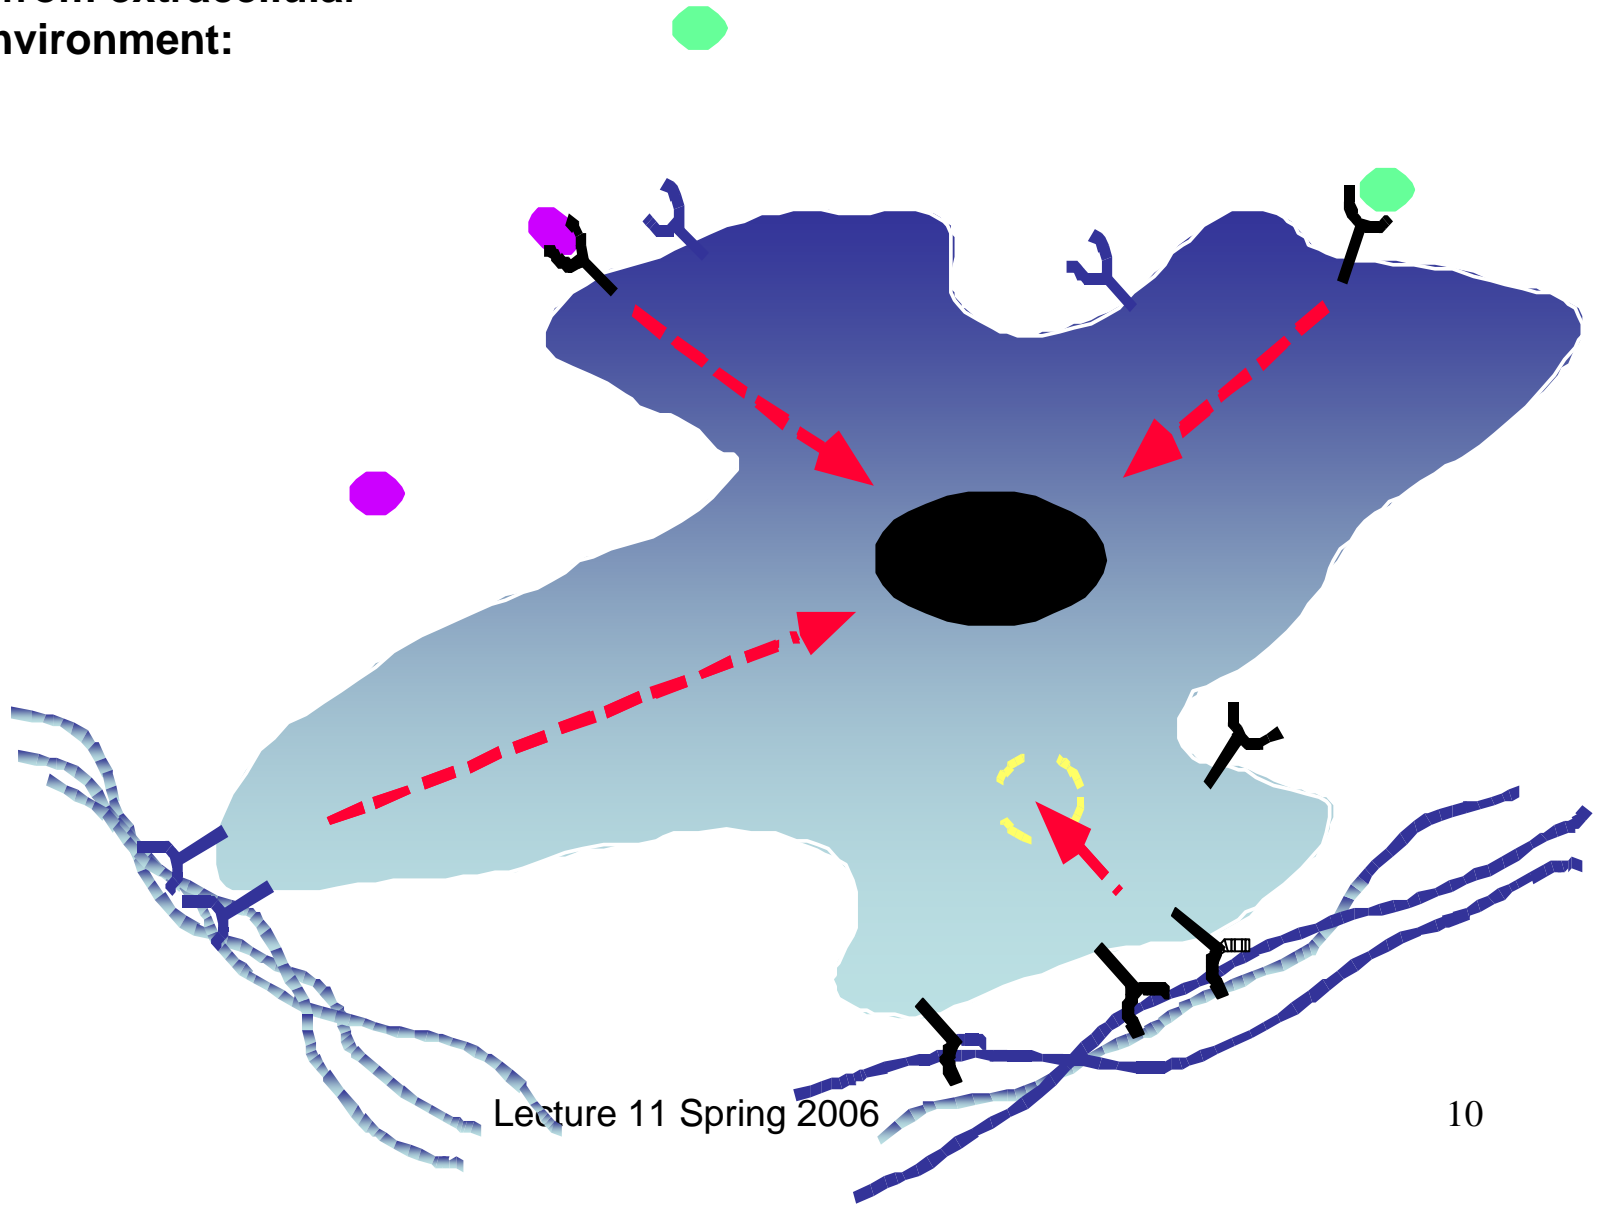

# Incorporation of ECM signals in biomaterials

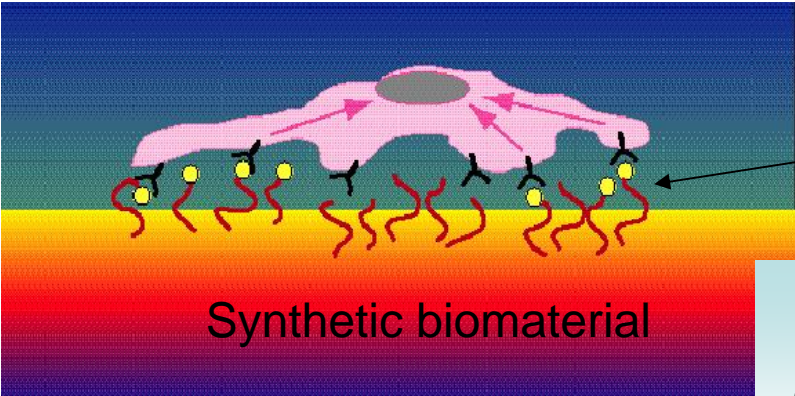


Peptides or proteins tethered to biomaterial surface, examples of (1) and (3)

Synthetic biomaterial

1. Cell adhesion/migration
2. Matrix remodeling
3. Cytokine signaling

(2) Matrix remodeling:

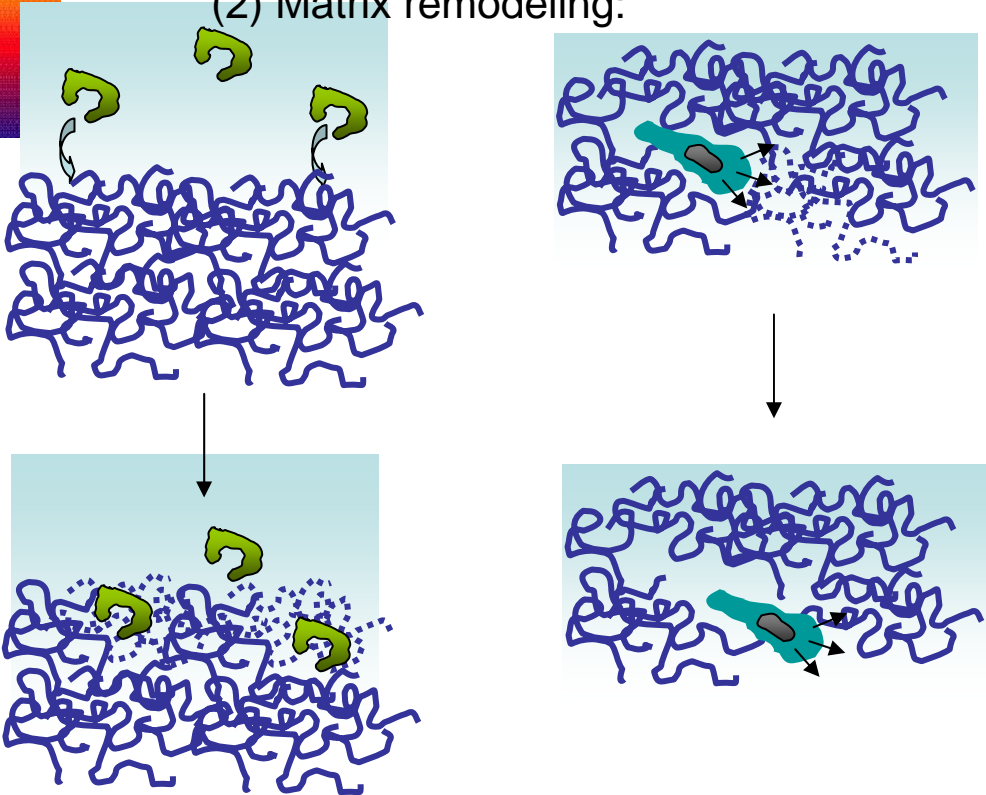

The insoluble surroundings of the cell:  
Functions of the native extracellular matrix (ECM):

# Collagen and Adhesions Proteins: Structure and Function

- Sixt et al. *Immunity* 22 (2005):19-25.
- Friedl et al. *Eur. J. Immunol.* 28 (1998): 2331.
- Lodish et al. *Molecular Cell Biology*


# Cell adhesion

# Controlling cell attachment and migration

Actin filaments (cytoskeleton)

integrin

Cell membrane

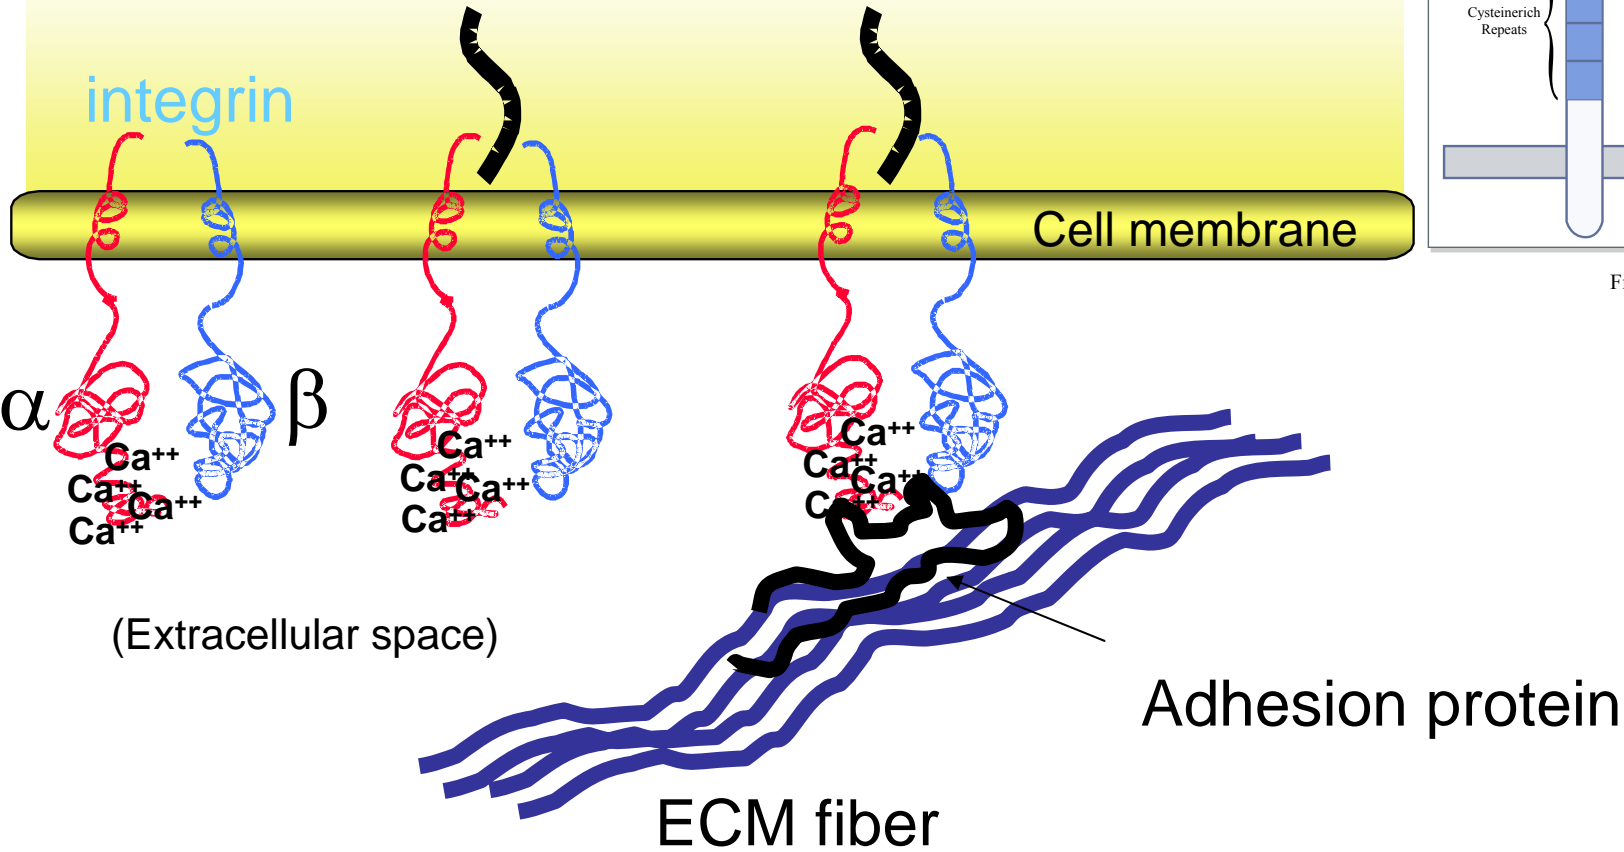

Structure of integrins:


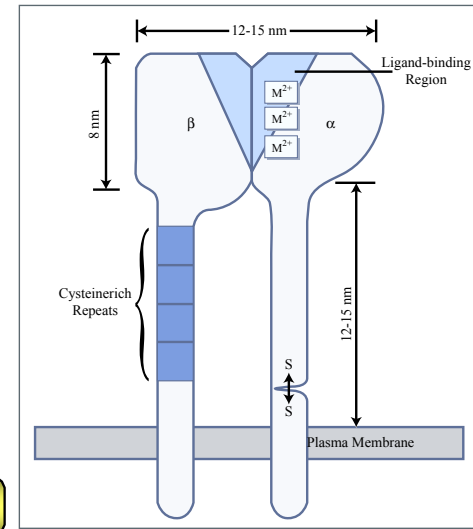


Figure by MIT OCW.



# Cell adhesion

Adhesive interactions can play multiple roles simultaneously: supporting adhesion, delivery of biochemical signals, or delivering biomechanical signals


(1)

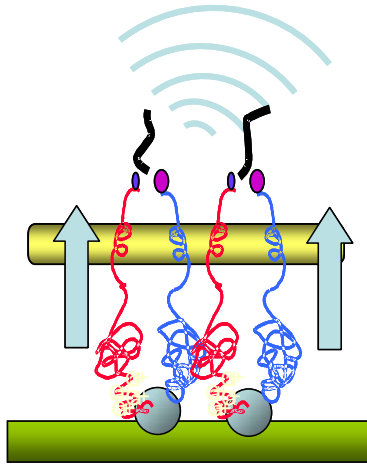

(2)

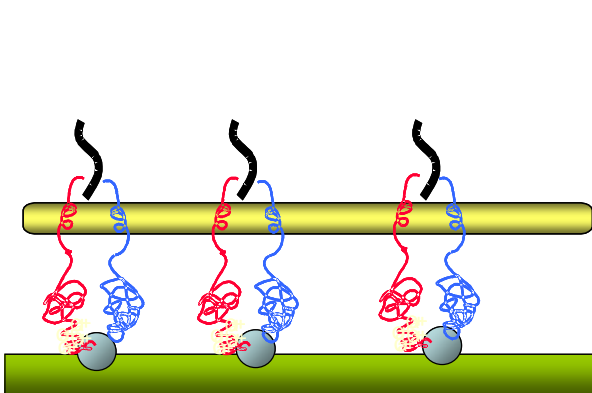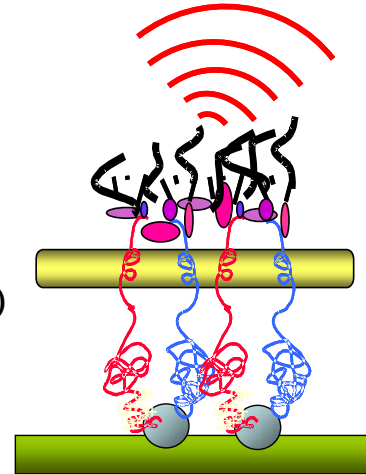

lipid membrane

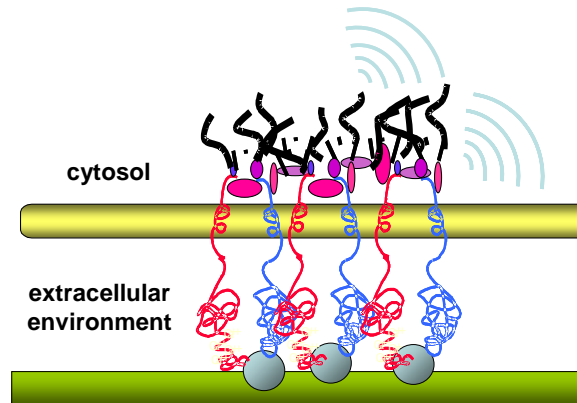

## Cell adhesion


Cells sense and respond to the stiffness of their substrate

(Discher, Janmey, Wang *Science* **310** 1139-1143 (2005))



# Cell adhesion on biomaterials:

Cell responses to non-biological, synthetic biomaterials

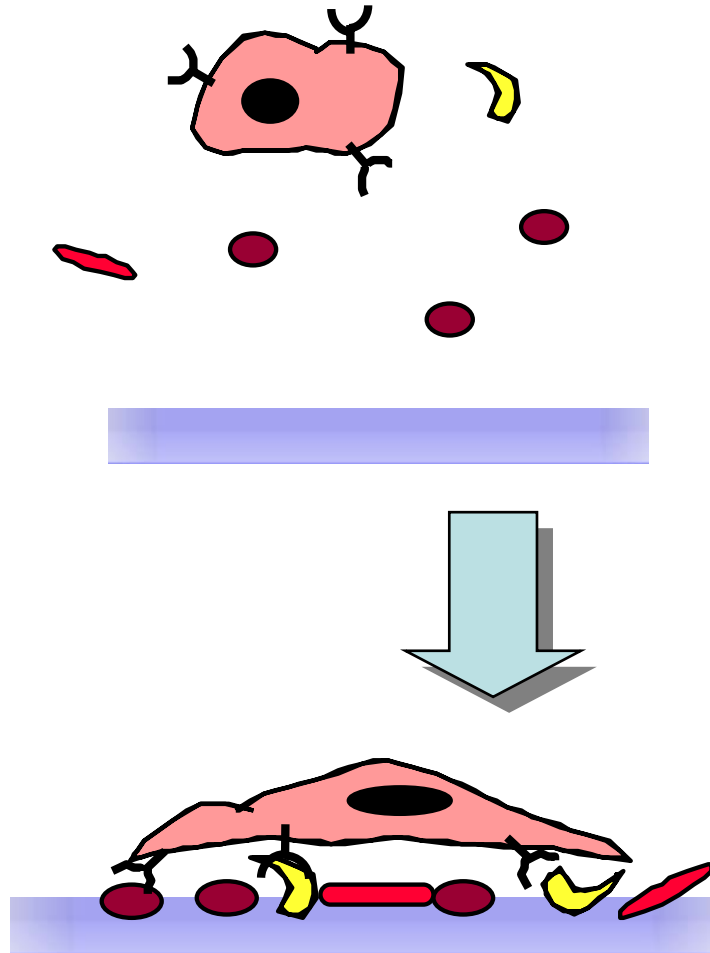

1. Protein adsorption
2. Denaturation (unfolding)?
3. Cell responses to expected and unexpected epitopes
4. Reorganization?
  - Vroman effect: protein exchange

# Control of cell attachment by mechanical properties of substrate

Polyelectrolyte multilayers (Rubner lab MIT):

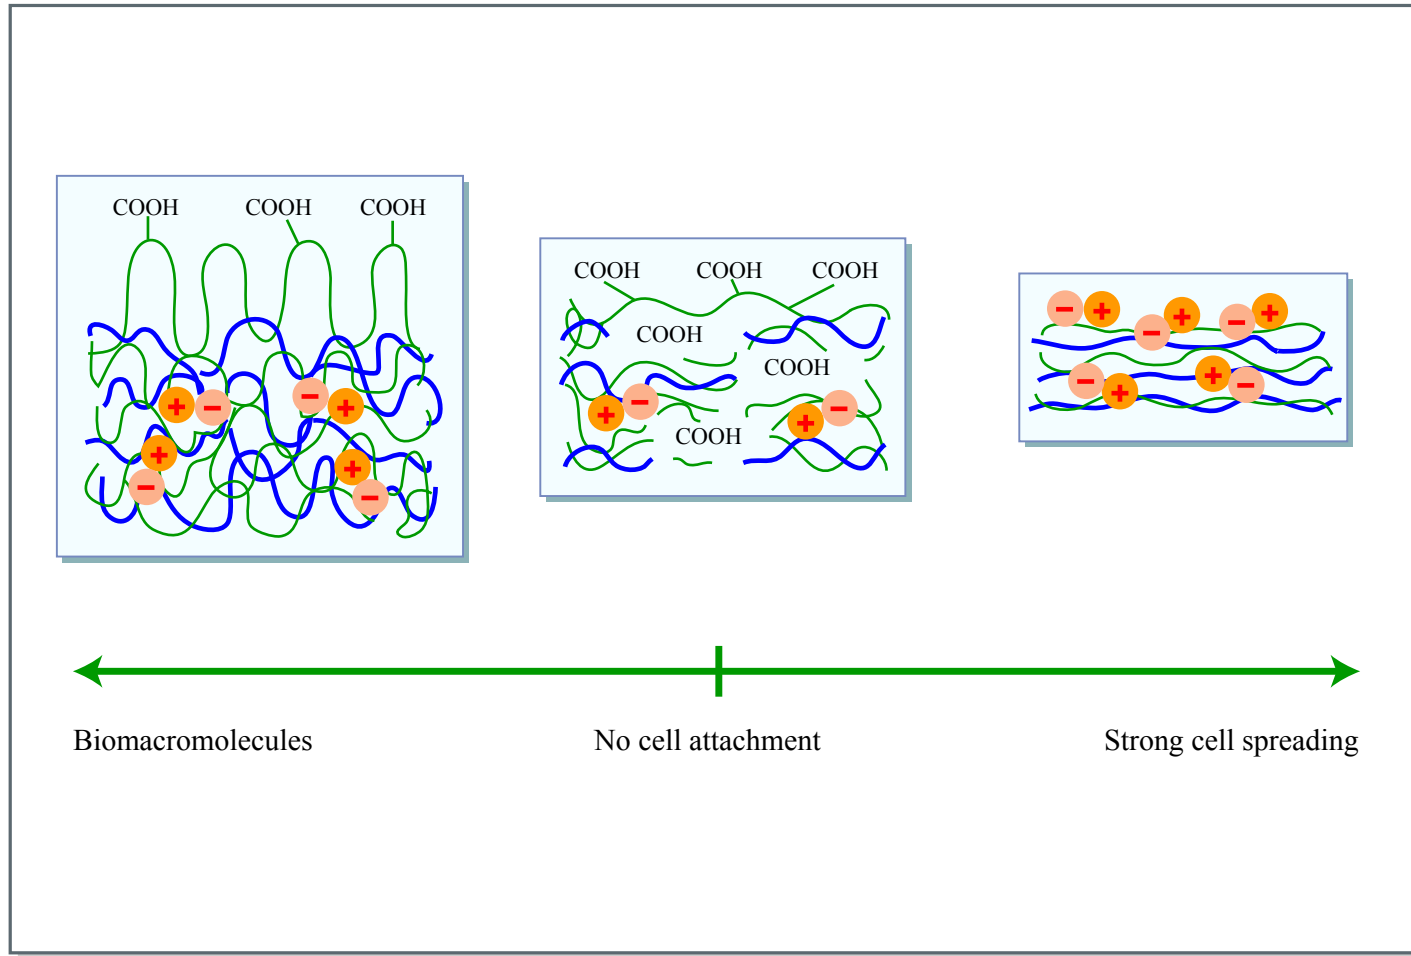


Figure by MIT OCW.

Lecture 11 Spring 2006


# Controlling cell response to biomaterials by building in ECM cues on a 'blank slate' background

# Design of protein adsorption-resistant surfaces


# Design of protein adsorption-resistant surfaces

# Limiting nonspecific cell adhesion

Methyl methacrylate

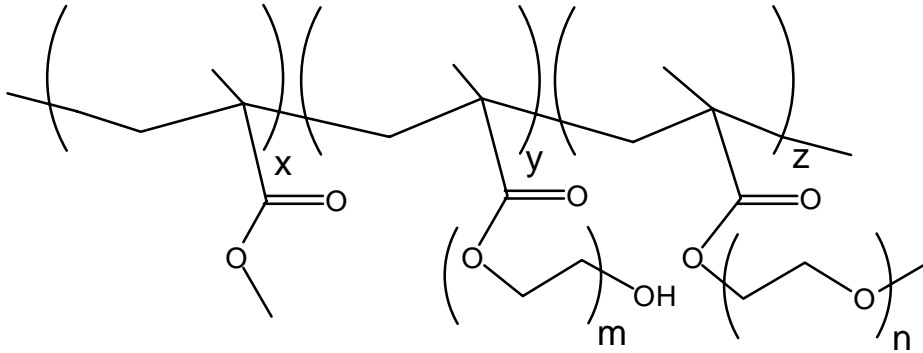

Poly(ethylene glycol)  
methacrylates

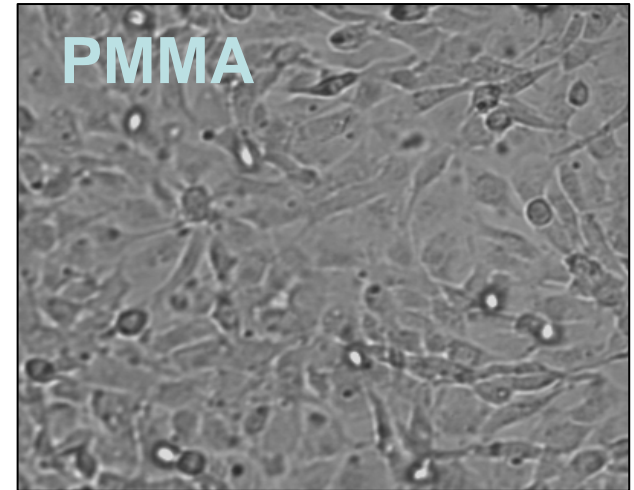

# Tailoring cell adhesion on biomaterials via immobilized ligands




- Peptide** integrin-binding GRGDSP sequence
- PEO** short 6-9 unit side chains for protein resistance
- PMMA** backbone anchors hydrophilic side chains

# Peptides used to modulate cell adhesion on biomaterials

Peptide sequence	Derived from	Conjugate receptor	Role
IKVAV	Laminin $\alpha$ -chain	LBP110 (110 KDa laminin binding protein)	Cell-ECM adhesion
RGD	Laminin $\alpha$ -chain, fibronectin, collagen	Multiple integrins	Cell-ECM adhesion
YIGSR	Laminin $\beta$ 1-chain	$\alpha_1\beta_1$ and $\alpha_3\beta_1$ integrins	Cell-ECM adhesion
RNIAEIIKDI	Laminin $\gamma$ -chain	unknown	Cell-ECM adhesion
HAV	N-cadherin	N-cadherin	Cell-cell adhesion
DGEA	Type I collagen	$\alpha_2\beta_1$ integrin	Cell-ECM adhesion
VAPG	Elastase	Elastase receptor	Cell-ECM adhesion
KQAGDV	Fibrinogen $\gamma$ -chain	$\beta_3$ integrins	Cell-ECM adhesion



# Cell responses to RGD

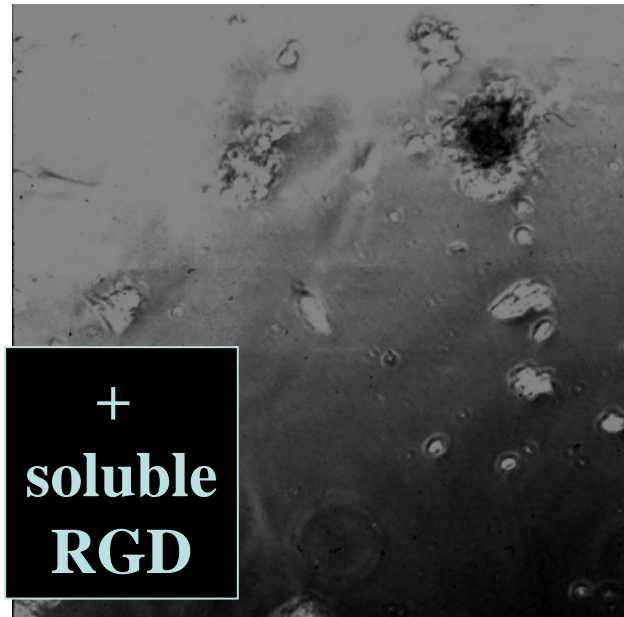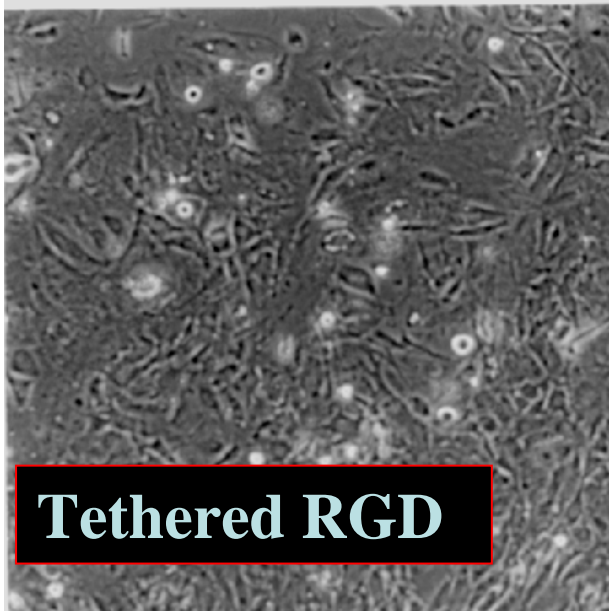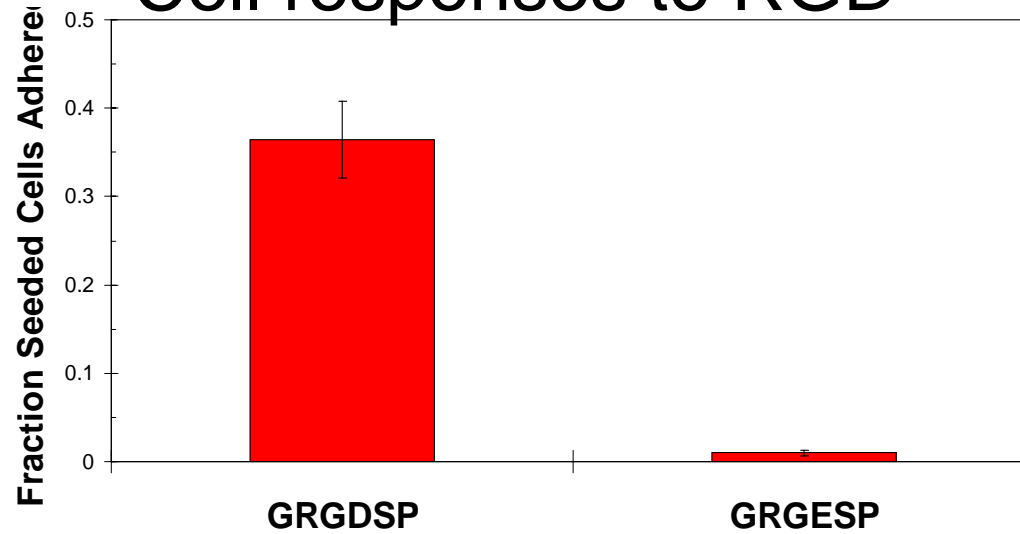

# Cells respond to control of ligand density at the surface

Figure 11 in Irvine, D. J., A. V. Ruzette, A. M. Mayes, and L. G. Griffith. "Nanoscale Clustering of RGD Peptides at Surfaces Using Comb Polymers. 2. Surface segregation of comb polymers in polylactide." *Biomacromolecules* 2 (2001): 545-56.

Figure 12 in Irvine, D. J., A. V. Ruzette, A. M. Mayes, and L. G. Griffith. "Nanoscale Clustering of RGD Peptides at Surfaces Using Comb Polymers. 2. Surface segregation of comb polymers in polylactide." *Biomacromolecules* 2 (2001): 545-56.

# Cells respond to control of ligand density at the surface

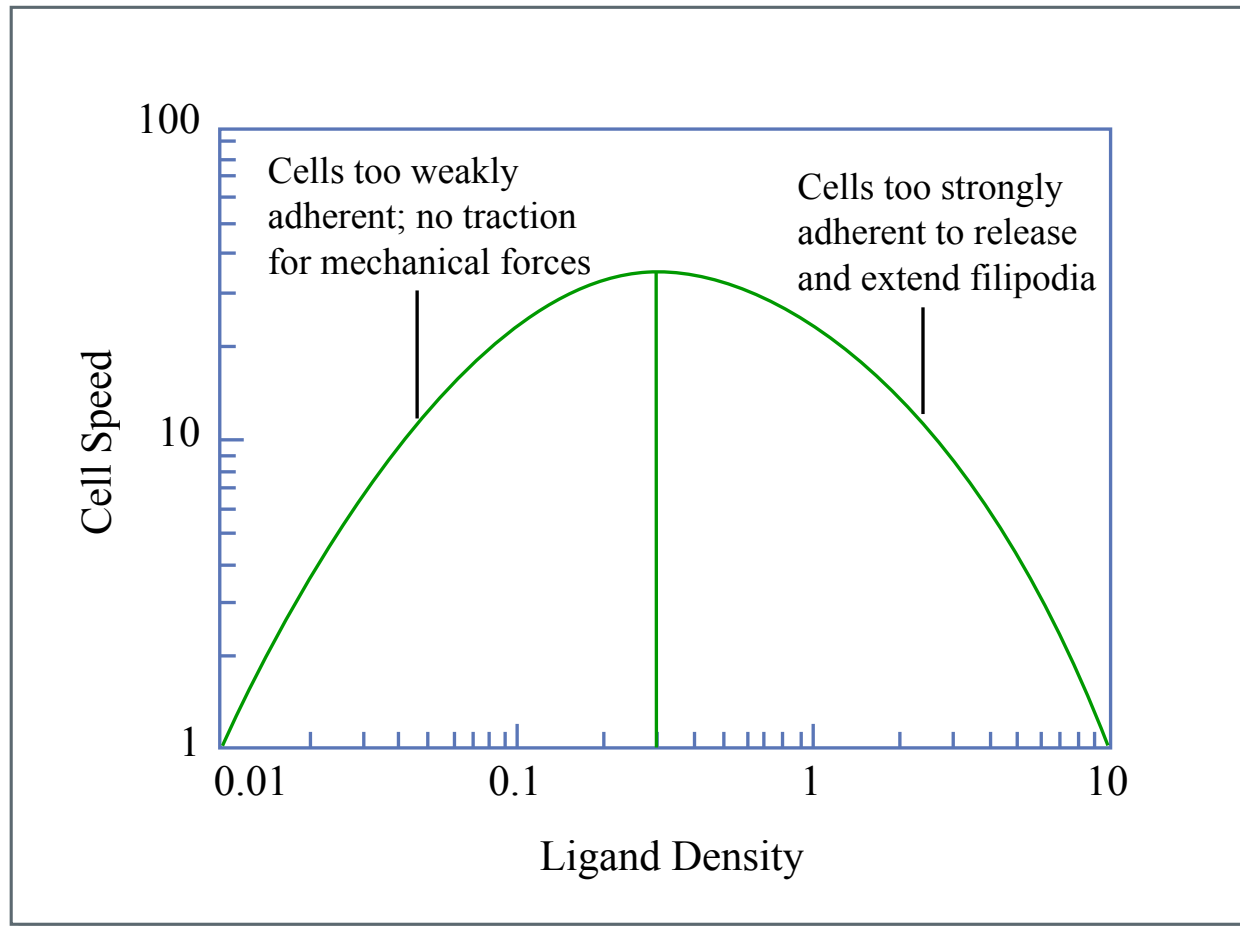


Figure by MIT OCW.

# Further Reading

1. Di Lullo, G. A., Sweeney, S. M., Korkko, J., Ala-Kokko, L. & San Antonio, J. D. Mapping the ligand-binding sites and disease-associated mutations on the most abundant protein in the human, type I collagen. *J Biol Chem* **277**, 4223-31 (2002).
2. Lemire, J. M., Merrilees, M. J., Braun, K. R. & Wight, T. N. Overexpression of the V3 variant of versican alters arterial smooth muscle cell adhesion, migration, and proliferation in vitro. *J Cell Physiol* **190**, 38-45 (2002).
3. Hubbell, J. A., Massia, S. P. & Drumheller, P. D. Surface-grafted cell-binding peptides in tissue engineering of the vascular graft. *Ann N Y Acad Sci* **665**, 253-8 (1992).
4. Drumheller, P. D. & Hubbell, J. A. Polymer networks with grafted cell adhesion peptides for highly biospecific cell adhesive substrates. *Anal Biochem* **222**, 380-8 (1994).
5. Kuhl, P. R. & Griffith-Cima, L. G. Tethered epidermal growth factor as a paradigm for growth factor-induced stimulation from the solid phase. *Nat Med* **2**, 1022-7 (1996).
6. Cook, A. D. et al. Characterization and development of RGD-peptide-modified poly(lactic acid-co-lysine) as an interactive, resorbable biomaterial. *J Biomed Mater Res* **35**, 513-23 (1997).
7. Mann, B. K., Schmedlen, R. H. & West, J. L. Tethered-TGF-beta increases extracellular matrix production of vascular smooth muscle cells. *Biomaterials* **22**, 439-44 (2001).
8. de Gennes, P. G. Conformations of polymers attached to an interface. *Macromolecules* **13**, 1069-1075 (1980).
9. Milner, S. T. Polymer brushes. *Science* **251**, 905-914 (1991).
10. Mendelsohn, J. D., Yang, S. Y., Hiller, J., Hochbaum, A. I. & Rubner, M. F. Rational design of cytophilic and cytophobic polyelectrolyte multilayer thin films. *Biomacromolecules* **4**, 96-106 (2003).
11. Banerjee, P., Irvine, D. J., Mayes, A. M. & Griffith, L. G. Polymer latexes for cell-resistant and cell-interactive surfaces. *J Biomed Mater Res* **50**, 331-9. (2000).
12. Irvine, D. J., Mayes, A. M. & Griffith, L. G. Nanoscale Clustering of RGD Peptides at Surfaces Using Comb Polymers. 1. Synthesis and Characterization of Comb Thin Films. *Biomacromol.* **2**, 85-94 (2001).
13. Irvine, D. J. et al. Comparison of tethered star and linear poly(ethylene oxide) for control of biomaterials surface properties. *J Biomed Mater Res* **40**, 498-509. (1998).
14. Irvine, D. J., Ruzette, A. V., Mayes, A. M. & Griffith, L. G. Nanoscale clustering of RGD peptides at surfaces using comb polymers. 2. Surface segregation of comb polymers in polylactide. *Biomacromolecules* **2**, 545-56 (2001).
15. Patel, N. et al. Spatially controlled cell engineering on biodegradable polymer surfaces. *Faseb Journal* **12**, 1447-1454 (1998).
16. Palecek, S. P., Loftus, J. C., Ginsberg, M. H., Lauffenburger, D. A. & Horwitz, A. F. Integrin-ligand binding properties govern cell migration speed through cell-substratum adhesiveness. *Nature* **385**, 537-40 (1997).